

TECHNICAL DATA SHEET

TECHNYL PROTECT C 30H1 V30 NC/F
(Previously TECHNYL C 30H1 V30 NATURAL/F)

TECHNYL PROTECT C 30H1 V30 NC/F is a flame retardant polyamide PA6, reinforced with 30% of glass fibre, for injection moulding. This grade has good mechanical properties, flame retardant rating UL94 V0 and glow-wire at 960°C.

General

Feature	UL V0 Good stiffness	Flame retarded
Polymer type	PA6 (Polyamide 6)	
Processing technology	Injection molding	
Colors available	Natural	
Forms	Pellets	

Product identification

ISO 1043 abbreviation	PA6,GF30FR(17)
ISO 16396 designation	PA6,GF30FR(17),M1,S14-120

Condition	Standard	Unit	Value
-----------	----------	------	-------

Physical properties

Condition	Standard	Unit	Value
Density	ISO 1183	g/cm ³	1.62
Molding shrinkage, parallel	ISO 294-4, 2577	%	0.1 - 0.2
Molding shrinkage, normal	ISO 294-4, 2577	%	0.6 - 0.7

Mechanical properties

Condition	Standard	Unit	Value	
Tensile modulus	1 mm/min	ISO 527-1/-2	MPa	12000 / 9100
Stress at break		ISO 527-1/-2	MPa	125 / 90
Strain at break		ISO 527-1/-2	%	1.7 / 2.3
Flexural modulus, ISO 178	2 mm/min	ISO 178	MPa	11000 / -
Flexural strength, ISO 178	2 mm/min	ISO 178	MPa	220 / -
Charpy impact strength, +23°C	+23°C	ISO 179/1eU	kJ/m ²	37 / 40
Charpy impact strength, -30°C	-30°C	ISO 179/1eU	kJ/m ²	30 / -
Charpy notched impact strength, +23°C	+23°C	ISO 179/1eA	kJ/m ²	9 / 13

TECHNICAL DATA SHEET

TECHNYL PROTECT C 30H1 V30 NC/F

	Condition	Standard	Unit	Value
Thermal properties				
Melting temperature, 10°C/min		ISO 11357-1	°C	222
Temp. of deflection under load, 1.80 MPa	1.80 MPa	ISO 75	°C	197

Burning behaviour


Flammability, 0.75 mm	0.75 mm	UL 94		V0
Flammability, 1.5 mm	1.5 mm	UL 94		V0
Flammability, 3.0 mm	3.0 mm	UL 94		V0
Glow-wire flammability index, GWFI, 0.75 mm	0.75 mm	IEC 60695-2-12	°C	960
Glow-wire flammability index, GWFI, 1.5 mm	1.5 mm	IEC 60695-2-12	°C	960
Glow-wire ignition temperature, GWIT, 0.75 mm	0.75 mm	IEC 60695-2-13	°C	825
Glow-wire ignition temperature, GWIT, 1.5 mm	1.5 mm	IEC 60695-2-13	°C	850
Burning rate, FMVSS, Thickness 1 mm		FMVSS 302		<100

*: conditioned according to ISO 1110

Processing conditions


Suggested max moisture	0.12 %
Rear temperature	230 - 240 °C
Middle temperature	240 - 250 °C
Front temperature	240 - 255 °C
Recommended mould temperature	80 - 100 °C

Stress-strain, dry

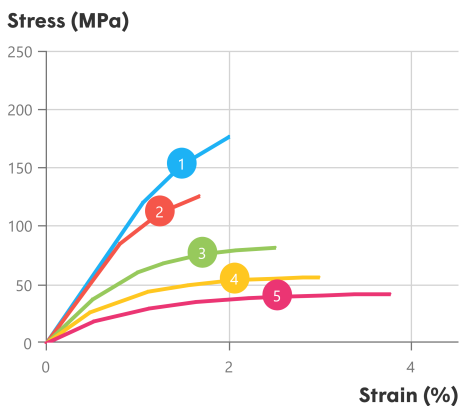

Temperature (°C)	
1	Spannung 1
2	Spannung 2
3	Spannung 3
4	Spannung 4
5	Spannung 5

Stress-strain, conditioned

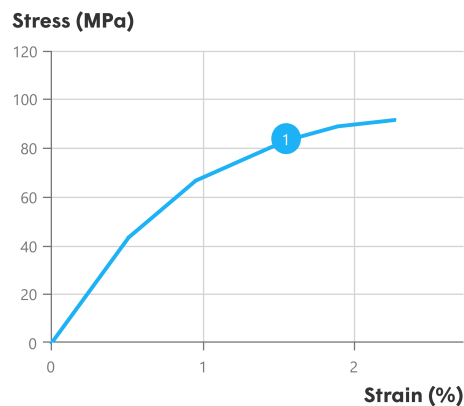

Temperature (°C)	
1	Spannung 1

Injection notes

The material is supplied in airtight bags, ready for use. In case that the virgin material has absorbed moisture, it must be dried with a dehumidified air drying equipment, dew point minimum -20°C. Recommended time 2-4h.

Injection advice

All reinforced, flame retardant compounds generate some level of abrasion/corrosion to the steel processing equipment. These issues may be magnified by using incorrect processing conditions (temperatures, residence time, moisture level ...) during the moulding process. Therefore, Domo recommends you adhere to the processing conditions detailed in this technical data sheet. For equipment that comes into contact with molten flame retardant compounds, Domo advises you to use a steel with high chromium and high carbon content (having a minimum concentration of 16% chromium) to prevent corrosion and abrasion. For the correct reference of steel associated to flame retardant compounds' processing, please refer to your equipment manufacturers. In the case of high requirements on surface quality a mould temperature of up to 120°C can be considered. The processing parameters like processing temperatures are a recommendation and can be adjusted in function of injection machine size, part geometry / design.

Disclaimer

The information provided in this documentation corresponds to our technical knowledge at the date of its publication and do not constitute a specification. This information may be subject to revision at our discretion. Domo cannot anticipate all conditions under which this information and our products of other manufactures in combination with our products may be used. Domo accepts no responsibility for results obtained by the application of this information or for the safety and suitability of our products alone or in combination with other products. Users are advised to make their own tests to determine the safety and suitability of each product or product combination for their own purposes. Unless otherwise agreed in writing, Domo sells the product without warranties. Buyers and users assume all responsibility and liability for loss or damage arising from handling and use of our products, whether used alone or in combination with other products. Unless specifically indicated, the grades mentioned are not suitable for applications in the pharmaceutical/medical sector.